

**Giant anomalous Hall resistivity of the room temperature
ferromagnet Fe_3Sn_2 - a frustrated metal with the *kagomé-bilayer*
structure**

T. Kida,^{1,*} L. Fenner,² A. S. Wills,^{2,3} I. Terasaki,⁴ and M. Hagiwara¹

¹*KYOKUGEN, Osaka University, 1-3 Machikaneyama, Toyonaka, Osaka 560-8531, Japan*

²*Department of Chemistry, University College London,
20 Gordon Street, London, WC1H 0AJ, United Kingdom*

³*The London Centre for Nanotechnology,
17-19 Gordon Street, London WC1H 0AH, United Kingdom*

⁴*Department of Applied Physics, Waseda University,
3-4-1 Okubo, Shinjuku, Tokyo 169-8555, Japan*

(Dated: November 2, 2009)

Abstract

We have investigated magnetic and transport properties of the *kagomé-bilayer* ferromagnet Fe_3Sn_2 . A soft ferromagnetism and a large anomalous Hall effect are observed. The saturated Hall resistivity of Fe_3Sn_2 is $3.2 \mu\Omega\text{cm}$ at 300 K, which is almost 20 times higher than that of typical itinerant-ferromagnets such as Fe and Ni. The anomalous Hall coefficient R_s is $6.7 \times 10^{-9} \Omega\text{cm/G}$ at 300 K, which is three orders of magnitude larger than that of pure Fe. R_s obeys an unconventional scaling to the longitudinal resistivity, ρ_{xx} , of $R_s \propto \rho_{xx}^{3.3}$. Such a relationship cannot be explained by the skew and/or side-jump mechanisms and indicates that the origin of the anomalous Hall effect in the frustrated magnet Fe_3Sn_2 is indeed extraordinary.

PACS numbers: 72.20.My, 75.47.-m, 75.50.Bb

INTRODUCTION

The Hall effect is the sideways deflection of an electron current due to an off-diagonal coupling between electric and magnetic field [1]. In itinerant ferromagnets, such as Fe or Ni, the presence of a spontaneous magnetization allows the effect to occur in the absence of an external magnetic field leading to a giant Hall resistivity, termed the anomalous Hall effect (AHE). Understanding this phenomenon and its origins are amongst the most fundamental and long term problems in condensed matter physics [1, 2, 3].

In itinerant ferromagnets the Hall resistivity (ρ_H) consists of two contributions:

$$\rho_H = -\rho_{xy} = R_0 H_{\text{ext}} + 4\pi R_1 M, \quad (1)$$

where $R_1 = (1 - N_d)R_0 + R_s$, R_0 is the ordinary Hall coefficient, R_s the anomalous Hall coefficient, H_{ext} the external magnetic field, M the magnetization, and N_d the demagnetizing factor. The first term of the right-hand side in Eq. (1) represents the ordinary Hall effect. The second term is in proportion to the magnetization and represents the AHE. The origins of the AHE are commonly separated into extrinsic and intrinsic mechanisms, though these were both first considered to be based on spin-orbit coupling and the spin polarization of conduction electrons. The extrinsic mechanisms are skew-scattering, where spin-orbit coupling breaks the left-right symmetry of the Mott scattering of charge carriers by an impurity [4], and side-jump scattering, which corresponds to a lateral displacement of an electron perpendicular to the direction of its spin and wavevector [5]. An example of an intrinsic mechanism is that proposed by Karplus and Luttinger [3] based on a ferromagnetic Hamiltonian with spin-orbit coupling. The eigenstates of such a system have the form of translationally invariant Bloch waves that interact through the interband matrix elements of the current operator, leading to an anomalous Hall current when the two spin states are unequal, *i.e.* under the condition for ferromagnetism. Recently, alternative mechanisms for the intrinsic AHE in conventional ferromagnets has been suggested based on a Berry phase that arises as conduction electrons move through non-trivial spin configurations [6, 7, 8, 9] and the orbital Aharonov-Bohm effect [10, 11], giving new directions for research into this extraordinary effect.

Much interest was generated from the observation of the AHE in the pyrochlore ferromagnet $\text{Nd}_2\text{Mo}_2\text{O}_7$, as it was argued that the chiral magnetic ordering gave rise to a Berry phase in the electronic scattering [12, 13]. Recent studies have, however, cast doubt on

this explanation, as the changes to the AHE appear not to follow those to the magnetic structure induced by a magnetic field [14, 15]. It therefore appears that other qualities are responsible for the AHE in $\text{Nd}_2\text{Mo}_2\text{O}_7$, presumably related to spin frustration - the competition between magnetic interactions. Its purest realization is in the geometrically frustrated magnets, where exchange geometries based on triangular plaquettes hinder the formation of conventional Néel order and allow the formation of a wide variety of exotic ground states, such as the quantum spin fluid [16, 17], topological spin glass [18, 19, 20, 21, 22], and partially ordered spin structures [23, 24]. The influences of spin frustration in frustrated ferromagnets is less well understood due to the scarcity of model systems. Despite this, the work on frustrated ferromagnets with localized spins, the spin ices [25, 26, 27, 28, 29] shows clearly the wealth of exotic behavior that can be hosted by frustrated ferromagnetic states [30, 31]. The challenge is now to develop an understanding of how geometric frustration enriches the physics that results from coupling the dual characters of localized spins and itinerant electrons, and effects such as the Kondo effect [32] or the competition between itinerant and dipole anisotropies [33, 34, 35].

The itinerant ferromagnet Fe_3Sn_2 , where the Fe-ions make up a *kagomé-bilayer* structure, was recently proposed as a model system with which to explore the interplay between conduction electrons, localized spins and spin frustration [36]. While this intermetallic material has been known for some time [37, 38, 39, 40, 41, 42], its recent reexamination as a frustrated itinerant ferromagnet lead to the discovery of a re-entrant spin glass phase below $T_g \sim 60$ K and the suggestion of a non-trivial canted ferromagnetic spin structure that rotates slowly from the *kagomé* planes towards the *c*-axis upon warming from ~ 60 K to near the high temperature ferromagnetic transition $T_c \simeq 640$ K [36]. In this work, we have investigated the magnetotransport properties of Fe_3Sn_2 in the intermediate non-trivial ferromagnetic regime where the moments are rotated away from the *c*-axis and show it to possess an anomalously large R_s that cannot be understood in terms of the conventional AHE mechanisms. These results, suggest clearly that an alternative mechanism is responsible for the AHE in this frustrated magnet.

EXPERIMENTAL

Polycrystalline samples of Fe_3Sn_2 were prepared following the method given in Ref. 36. Laboratory X-ray diffraction analysis of the samples showed a small amount of FeSn and FeSn_2 impurity phases (5 % at maximum). As these materials are antiferromagnets, they are not expected to have a significant effect on the measured data shown below. We prepared the sample for the transport measurements by cutting from a pressed pellet a monolith with dimensions of $4.0 \times 1.0 \times 0.5 \text{ mm}^3$. The magnetization measurements were performed by using a commercial SQUID magnetometer (MPMS-XL7, Quantum Design, Inc.) in magnetic fields up to 7 T. The electrical resistivity was measured between 2 and 300 K by a conventional dc four-probe method with a current of 1 mA. The Hall resistance was measured between 100 and 300 K in magnetic fields up to 7 T. In the Hall resistance measurements, the Hall voltage V_H at each measured temperature was determined from the measured voltage $V(H_{\text{ext}}, I)$ as $V_H(H_{\text{ext}}) = (1/4)(V(H_{\text{ext}}, I) - V(H_{\text{ext}}, -I) + V(-H_{\text{ext}}, -I) - V(-H_{\text{ext}}, I))$ so that unwanted signals from misalignments of the contact electrodes and from thermoelectric voltages were canceled.

RESULTS AND DISCUSSION

Previous work has show this sample of Fe_3Sn_2 to display ferromagnetic ordering at $T_c = 640 \text{ K}$, a slow rotation of Fe-moments from the c -axis towards the kagome plane on cooling down to 60 K, and a re-entrant spin glass phase below $T_g \sim 60 \text{ K}$ [36]. The rotation of the moments from the c -axis is notable as it involves relaxation of the rules that the moments are collinear and equal, and instead allows the formation of a non-trivial ferromagnetic phase in which the moments are not collinear and differ in magnitude. This complexity of the magnetic order is expected to be partly responsible for the formation of the low temperature spin glass phase and may be the origin of the AHE presented in this study.

The magnetization curves as a function of the effective magnetic field H_{eff} in the temperature range between 100 and 300 K are shown in Fig. 2(a), where $H_{\text{eff}} = H_{\text{ext}} - 4\pi N_d M$. The value of the demagnetization correction $N_d (= 0.5667)$ is calculated following work on rectangular prisms by Chen *et al* [43]. A rapid saturation and a weak remanent-magnetization are observed. The value of the saturation magnetization M_s estimated by the Arrott plot (M^2 vs

H_{eff}/M) method is $2.0 \mu_B/\text{Fe}$ at 100 K, in good agreement with literature values [36, 40, 41].

The electrical resistivity, ρ_{xx} , of Fe_3Sn_2 shows a metallic temperature dependence, and is $0.8 \text{ m}\Omega\text{cm}$ at 300 K. The residual resistivity ratio (RRR) defined as $\rho_{xx}(300 \text{ K})/\rho_{xx}(4 \text{ K})$, is close to 4. This value is much smaller than that of pure Fe and Ni [44] and indicates that the impurity and/or a grain-boundary scatterings are significant in this polycrystalline sample of Fe_3Sn_2 .

The magnetic field dependence of ρ_H is shown in Fig. 2(b) for Fe_3Sn_2 in the temperature range between 100 and 300 K. The shape of the ρ_H - H_{eff} curves is very similar to that of the magnetization curves, *i.e.*, a rapid increase from $\mu_0 H_{\text{eff}} = 0$ to 0.5 T and a saturation in higher magnetic fields. The saturated value of ρ_H is $3.2 \mu\Omega\text{cm}$ at 300 K, that is almost 20 times higher than that of typical itinerant-ferromagnets Fe [44] and Ni [45], and is comparable to that of the pyrochlore molybdate $\text{Nd}_2\text{Mo}_2\text{O}_7$ at low temperatures [46].

Substituting $R_1 = (1 - N_d)R_0 + R_s$ into Eq. (1), and division of both sides by H_{eff} , gives the following expression:

$$\rho_H/H_{\text{eff}} = R_0 + 4\pi(R_0 + R_s)(M/H_{\text{eff}}). \quad (2)$$

This relation allows the extraction of the values of the ordinary Hall coefficient, R_0 , and the anomalous Hall coefficient, R_s , from the intercept and slope of ρ_H/H_{eff} plotted as a function of M/H_{eff} , respectively. The values of ρ_H/H_{eff} *vs.* M/H_{eff} for Fe_3Sn_2 in the temperature range 100-300 K are shown in Fig. 3. ρ_H/H_{eff} is highly linear in M/H_{eff} , indicating that the AHE contribution of Fe_3Sn_2 is proportional to the magnetization. For all temperatures, the value of $|R_0|$ is of the order of $10^{-12} \Omega\text{cm/G}$. The carrier density, n , estimated by $R_0 = |1/nec|$ (e is the elementary electric charge; c is the velocity of light.) is $10^{22} \sim 10^{23} \text{ cm}^{-3}$, which is in the range of n values of conventional metals including pure Fe and Ni [44]. In contrast, the value of R_s is $6.7 \times 10^{-9} \Omega\text{cm/G}$ at 300 K, and is three orders of magnitude larger than R_s of pure Fe [44] and Ni [45].

Figure 4 shows R_s as a function of reduced temperature T/T_c for the present sample, pure Ni, and Ni-Cu alloys [45]. For pure Ni, the R_s takes a maximum peak at around $0.9T_c$ (not shown in Fig. 4), and approaches towards zero below the peak [45]. For the ferromagnetic Ni-Cu alloys, a residual component of R_s is observed at low T/T_c and increases with increasing Cu concentration. For example, the R_s of $\text{Ni}_{0.9062}\text{Cu}_{0.0938}$ is $7 \times 10^{-12} \Omega\text{cm/G}$ at $T/T_c = 0.2$ and is almost 10 times higher than that of pure Ni. Although Fe_3Sn_2 shows nearly the

same residual resistivity ratio as of $\text{Ni}_{0.9062}\text{Cu}_{0.0938}$, the residual component of R_s is small. The small R_s at low temperature indicates that the residual resistivity does not affect R_s , and suggests that the origin of the large AHE on Fe_3Sn_2 cannot be explained by a simple extrinsic origin such as impurity effects.

Following to the preceding work by Miyasato *et al.* [9], we show in Fig. 5 the absolute values of $|\sigma_{xy}|$ as a function of σ_{xx} for the present sample (open circle) and for a range of other materials collated by Fukumura *et al.* [47], namely ferromagnetic (FM) pure metals, diluted magnetic semiconductors (DMSs), perovskite manganites $((\text{La},\text{A})\text{MnO}_3)$, and Co-doped rutile TiO_2 on the same figure. Fe_3Sn_2 shows $\sigma_{xx} \sim 10^3$ S/cm, and lies in the crossover region between metallic (10^4 S/cm $< \sigma_{xx} < 10^6$ S/cm) and hopping ($\sigma_{xx} < 10^4$ S/cm) regimes. While many other ferromagnetic materials classified within the hopping regime are semiconducting, the temperature dependence of the resistivity shows Fe_3Sn_2 to display metallic conduction (inset of Fig. 2a). Reflecting this extraordinary behavior, Fe_3Sn_2 does not obey the expected $\sigma_{xy} \propto \sigma_{xx}^{1.6}$ scaling (see open circles in Fig. 5).

Conventionally, the AHE has been characterized by the phenomenological relation between R_s and ρ_{xx} :

$$R_s = a\rho_{xx} + b\rho_{xx}^2, \quad (3)$$

where a and b are constants. The linear and the quadratic terms in ρ_{xx} are attributed to the skew-scattering [4] and the side-jump mechanism [5], respectively. In many experimental cases of the AHE, a simpler relationship is found in which R_s is proportional to ρ_{xx}^n , with the index lying in the range $n = 1 \sim 2$. In our case, the R_s of Fe_3Sn_2 does not obey Eq. (3) and is instead proportional to $\rho_{xx}^{3.3}$.

According to Eq. (3) a large ρ_{xx} , yields a large Hall resistivity. This scheme may provide a possible explanation for the large Hall resistivity of nanocomposite granular systems. As reported by Gao *et al.* [48], in co-sputtered $\text{Fe}_x\text{Sn}_{1-x}$ granular alloys a large saturated Hall resistivity is $8.68 \mu\Omega\text{cm}$ at room temperature and $\rho_H \propto \rho_{xx}^{3.4}$. Clearly more detailed studies, such as annealing effect and impurity-doping effect are needed to understand the observed relationship between R_s and ρ_{xx} .

CONCLUSIONS

In summary, we have measured the magnetization, electrical resistivity and Hall resistivity of a *kagomé-bilayer* ferromagnet Fe_3Sn_2 . A soft ferromagnetism and a large anomalous Hall effect are observed. The saturated Hall resistivity and the anomalous Hall coefficient of Fe_3Sn_2 are $3.2 \mu\Omega\text{cm}$ and $6.7 \times 10^{-9} \Omega\text{cm/G}$ at 300 K, respectively. The $\sigma_{xy} \propto \sigma_{xx}^{1.6}$ scaling seen in many other AHE materials is not observed for Fe_3Sn_2 polycrystalline sample. Instead, the R_s is found to be proportional to $\rho_{xx}^{3.3}$, suggesting that the AHE on Fe_3Sn_2 is both unconventional and intrinsic, *i.e.* it cannot be explained by the extrinsic effects of impurities. We speculate the origin of the effect is the non-trivial ferromagnetic structure and the frustration associated with the localized spins of the *kagomé-bilayer* structure.

Acknowledgments

This work was carried out under the foreign visiting researcher's program and the visiting researcher's program at KYOKUGEN in Osaka University. The authors thank Dr. K. Ogushi, Dr. K. Segawa, Prof. Y. Ando, Dr. W. Branford, and Prof. S. T. Bramwell for useful or fruitful discussion.

This study was supported in part by Grant-in-Aid for Scientific Research (B) (No. 20340089) and for Scientific Research on Priority Areas "High Field Spin Science in 100T" (No. 451) from MEXT, Japan. ASW and LF would also like to thank the Royal Society and EPSRC (grant number EP/C534654) for funding.

* Electronic address: kida@mag.cqst.osaka-u.ac.jp

- [1] C. M. Hurd, *The Hall Effect in Metals and Alloys* (Plenum Press, New York, 1972).
- [2] N. Nagaosa, J. Phys. Soc. Jpn. **75**, 042001 (2006).
- [3] R. Karplus and J. M. Luttinger, Phys. Rev. **95**, 1154 (1954).
- [4] J. Smit, Physica **21**, 877 (1955); *ibid.* **24**, 39 (1958).
- [5] L. Berger, Phys. Rev. **B2**, 4559 (1970).
- [6] J. Ye, Y. B. Kim, A. J. Millis, B. I. Shraiman, P. Majumdar, and Z. Tešanović, Phys. Rev. Lett. **83**, 3737 (1999).

- [7] M. Onoda and N. Nagaosa, J. Phys. Soc. Jpn. **71**, 19 (2002).
- [8] T. Jungwirth, Q. Niu, and A. H. MacDonald, Phys. Rev. Lett. **88**, 207208 (2002).
- [9] T. Miyasato, N. Abe, T. Fujii, A. Asamitsu, S. Onoda, Y. Onose, N. Nagaosa, and Y. Tokura, Phys. Rev. Lett. **99**, 086602 (2007).
- [10] H. Kontani, T. Tanaka, and K. Yamada, Phys. Rev. **B75**, 184416 (2007).
- [11] H. Kontani, T. Tanaka, D. S. Hirashima, K. Yamada, and J. Inoue, Phys. Rev. Lett. **100**, 096601 (2008).
- [12] Y. Taguchi, Y. Oohara, H. Yoshizawa, N. Nagaosa, and Y. Tokura, Science **291**, 2573 (2001).
- [13] Y. Taguchi, T. Sasaki, S. Awaji, Y. Iwasa, T. Tayama, T. Sakakibara, S. Iguchi, T. Ito, and Y. Tokura, Phys. Rev. Lett. **90**, 257202 (2003).
- [14] Y. Yasui, T. Kageyama, T. Moyoshi, M. Soda, M. Sato, and K. Kakurai, J. Phys. Soc. Jpn. **75**, 084711 (2006).
- [15] M. Sato, J. Magn. Magn. Mater. **310**, 1021(2007).
- [16] M. P. Shores, E. A. Nytko, B. M. Bartlett, and D. G. Nocera, J. Am. Chem. Soc. **127**, 13462 (2005).
- [17] R. H. Colman, C. Ritter, and A. S. Wills, Chem. Mater. **20**, 6897 (2008).
- [18] A. S. Wills, Can. J. Phys. **79**, 1501 (2001).
- [19] A. S. Wills, A. Harrison, C. Ritter, R. I. Smith, Phys. Rev. **B61**, 6156 (2000).
- [20] A. S. Wills, V. Depuis, E. Vincent, J. Hammann, R. Calemczuk, Phys. Rev. **B62**, R9264 (2000).
- [21] A. S. Wills, G. S. Oakley, D. Visser, J. Frunzke, A. Harrison, and K. H. Andersen, Phys. Rev. **B64**, 094436 (2001).
- [22] W. G. Bisson and A. S. Wills, J. Phys.: Condens. Matter. **20**, 452204 (2008).
- [23] J. D. M. Champion, A. S. Wills, T. Fennell, S. T. Bramwell, J. S. Gardner, and M. A. Green Phys. Rev. **B64**, 140407 (2001).
- [24] J. R. Stewart, G. Ehlers, A. S. Wills, S. T. Bramwell, and J. S. Gardner, J. Phys.: Condens. Matter. **16**, L321 (2004).
- [25] S. T. Bramwell and M. J. Harris, J. Phys.: Condens. Matter **10** L215 (1998).
- [26] M. J. Harris, S. T. Bramwell, and P. C. W. Holdsworth, Phys. Rev. Lett. **81**, 4496 (1998).
- [27] R. F. Wang, C. Nisoli, R. S. Freitas, J. Li, W. McConville, B. J. Cooley, M. S. Lund, N. Samarth, C. Leighton, V. H. Crespi, and P. Schiffer, Nature **439**, 303 (2006).

- [28] Y. Qi, T. Brintlinger, and J. Cumings, Phys. Rev. B **77**, 094418 (2008).
- [29] A. S. Wills, R. Ballou, and C. Lacroix, Phys. Rev. B **66**, 144407 (2002).
- [30] L. D. C. Jaubert, J. T. Chalker, P. C. W. Holdsworth, and R. Moessner, J. Phys.: Conf. Ser. **145**, 012024 (2009).
- [31] C. Castelnovo, R. Moessner, and S.L. Sondhi, Nature **451**, 42 (2008).
- [32] J. Kondo, Prog. Theoret. Phys. **32**, 37 (1964).
- [33] L. Deakin, M. J. Ferguson, A. Mar, J. E. Greedan, and A. S. Wills, Chem. Mater. **13**, 1407 (2001).
- [34] M. Richter, J. Rusz, H. Rosner, K. Koepernik, I. Opahle, U. Nitzsche, and H. Eschrig, J. Magn. Magn. Mater. **272-276**, e251 (2004).
- [35] M. Inamdar, A. Thamizhavel, and S. Ramakrishnan, J. Alloys Compounds **480**, 28 (2009).
- [36] L. Fenner, A. A. Dee, and A. S. Wills, J. Phys.: Condens. Matter, *submitted* (2009).
- [37] O. Nial, Svensk. Kern. Tidsk. **59**, 165 (1947).
- [38] G. Trumpy, E. Both, C. Djéga-Mariadassou, and P. Lecocq, Phys. Rev. B **2**, 3477 (1970).
- [39] B. Malaman, B. Roques, A. Courtois, and J. Protas, Acta Cryst. B **32**, 1348 (1976).
- [40] B. Malaman, D. Fruchart, and G. L. Caër, J. Phys. F: Metal Phys. **8**, 2389 (1978).
- [41] G. L. Caër, B. Malaman, and B. Roques, J. Phys. F: Metal Phys. **8**, 323 (1978).
- [42] G. L. Caër, B. Malaman, L. Häggström, and T. Ericsson, J. Phys. F: Metal Phys. **9**, 1905 (1979).
- [43] D.-X. Chen, E. Pardo, and A. Sanchez, IEEE Trans. Magn. **38**, 1742 (2002).
- [44] N. V. Volkenshtein and G. V. Fedorov, Soviet Phys. JETP **11**, 48 (1960).
- [45] S. N. Kaul, Phys. Rev. B **20**, 5122 (1979).
- [46] S. Yoshii, S. Iikubo, T. Kageyama, K. Oda, Y. Kondo, K. Murata, and M. Sato, J. Phys. Soc. Jpn. **69**, 3777 (2000).
- [47] T. Fukumura, H. Toyosaki, K. Ueno, M. Nakano, T. Yamasaki, and M. Kawasaki, Jpn. J. Appl. Phys. **46**, L642 (2007).
- [48] J. Gao, F. Wang, X. Jiang, G. Ni, F. Zhang, and Y. Du, J. Appl. Phys. **93**, 1851 (2003).

Figures

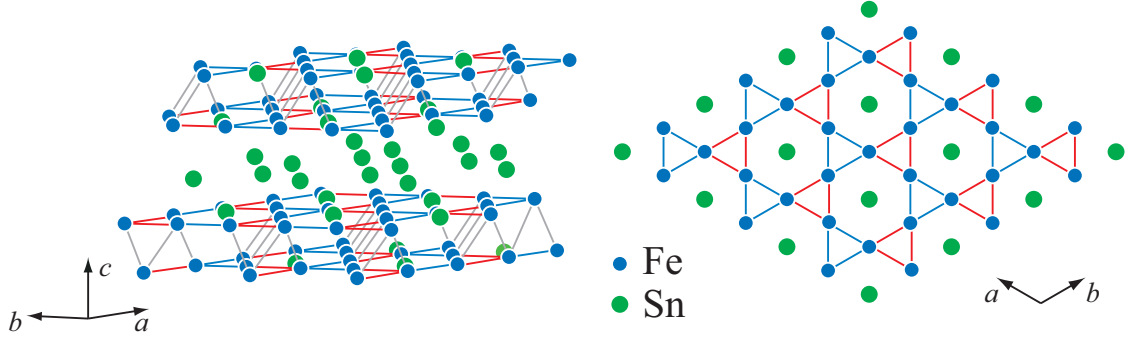


FIG. 1: The crystal structure of Fe_3Sn_2 is made up of Fe/Sn bilayers separated by Sn. The Fe ions form a *kagomé-bilayer* structure made up of 2 sizes of equilateral triangles shown in red and blue (color online) [36].

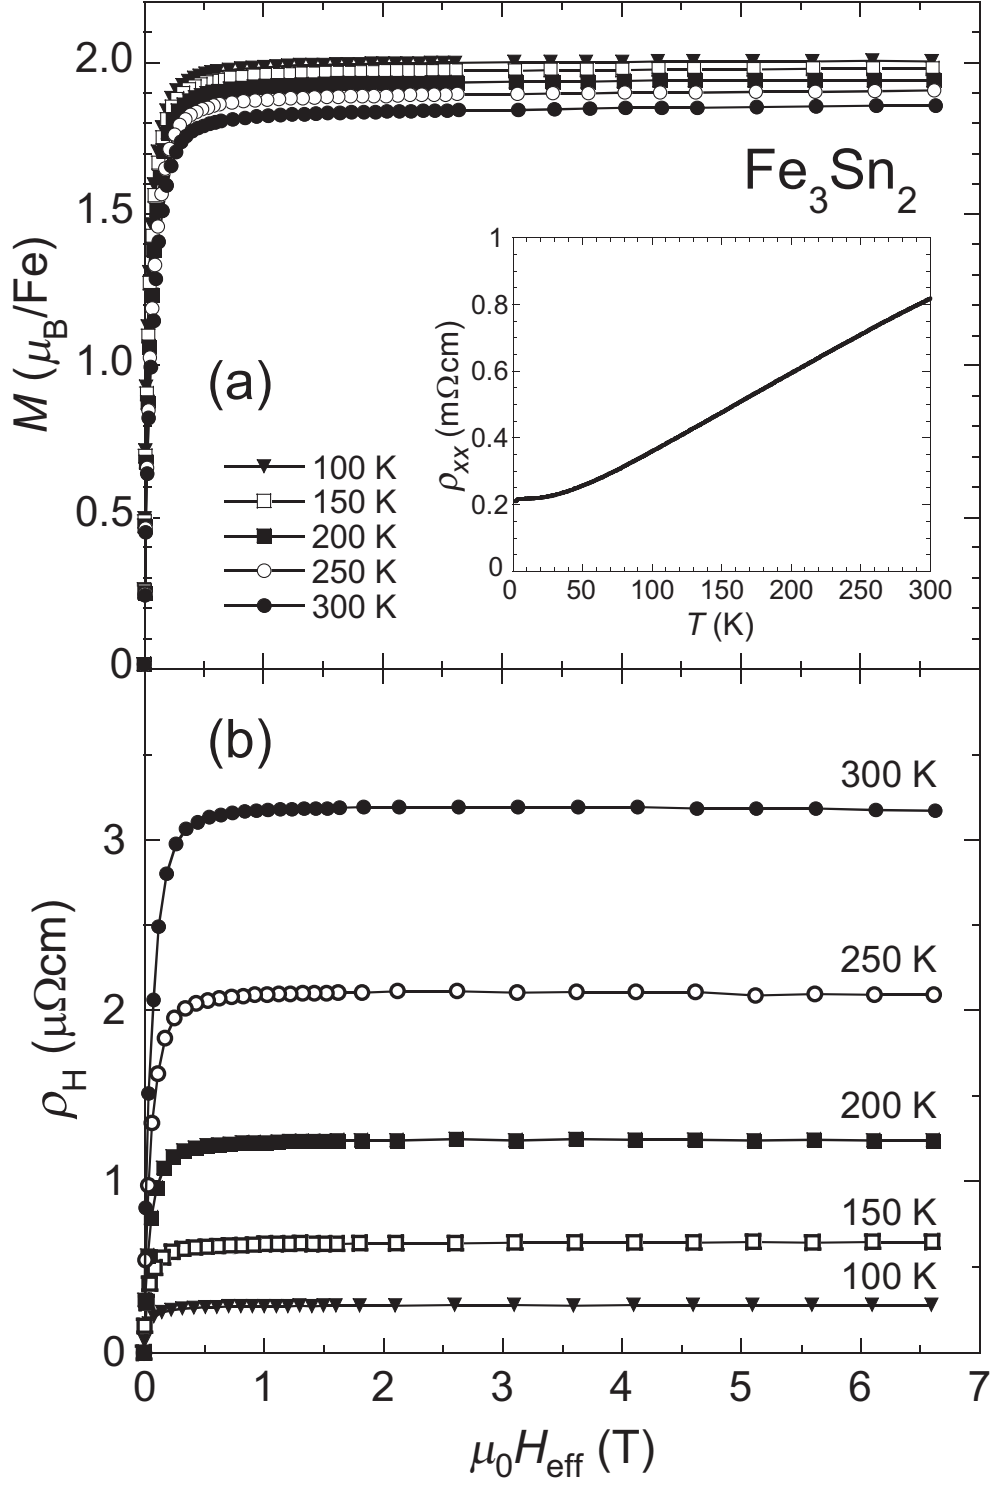


FIG. 2: (a) Magnetic field dependence of magnetization at various temperatures. The inset shows the temperature dependence of the electrical resistivity ρ . (b) Magnetic field dependence of the Hall resistivities for a Fe_3Sn_2 polycrystalline sample at various temperatures.

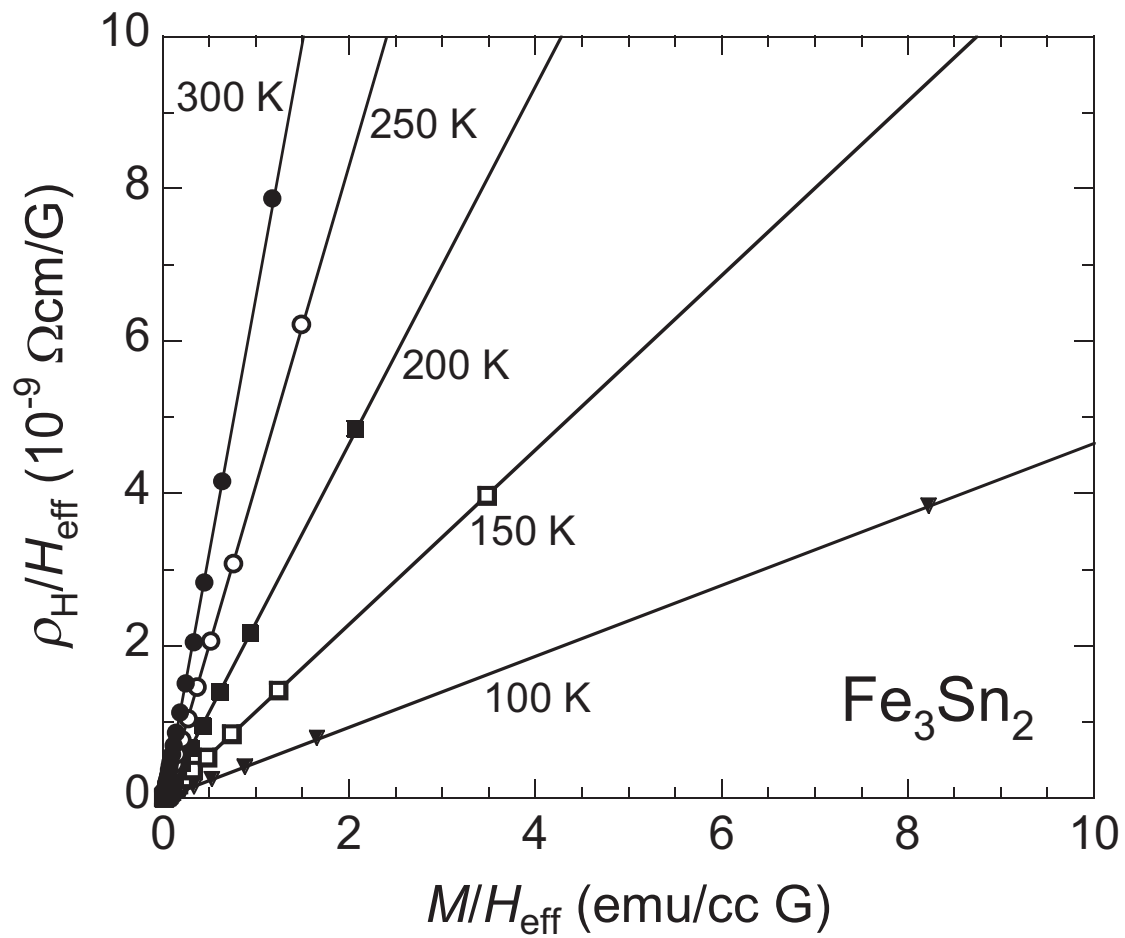


FIG. 3: ρ_H/H_{eff} vs M/H_{eff} at various temperatures.

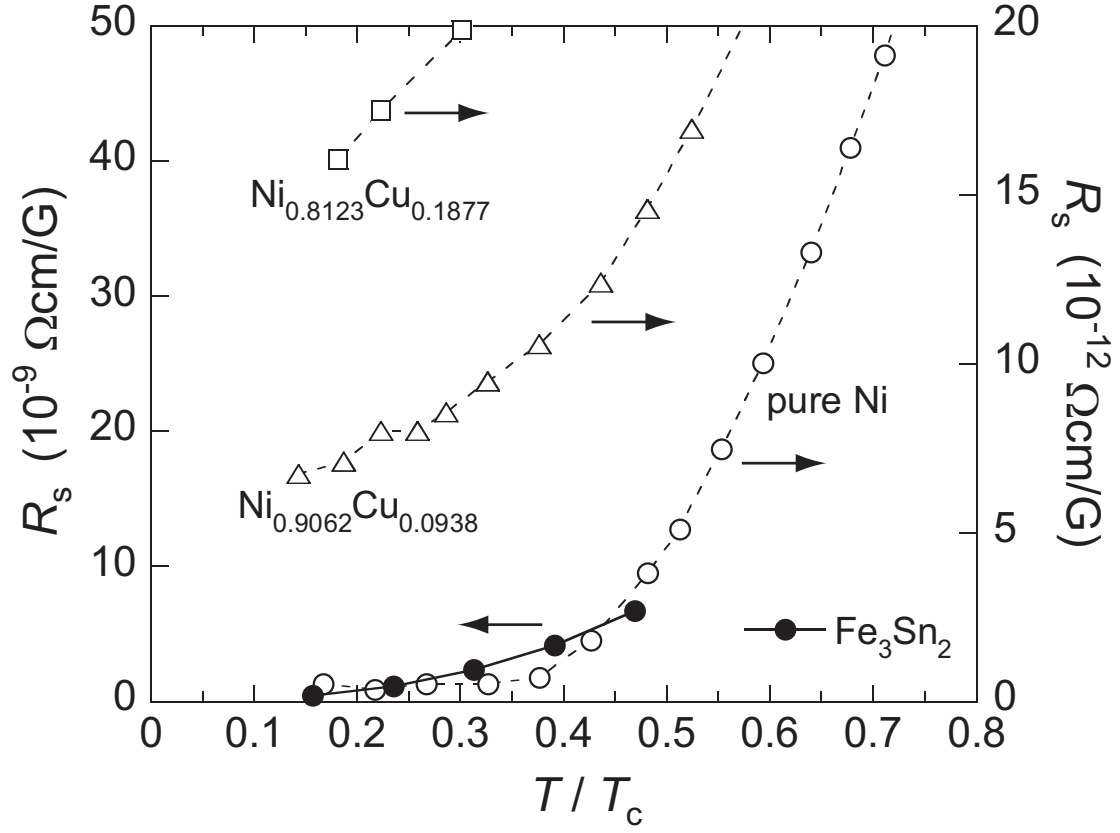


FIG. 4: Anomalous Hall coefficient (R_s) as a function of reduced temperature (T/T_c) for Fe_3Sn_2 , pure Ni, and Ni-Cu alloys.

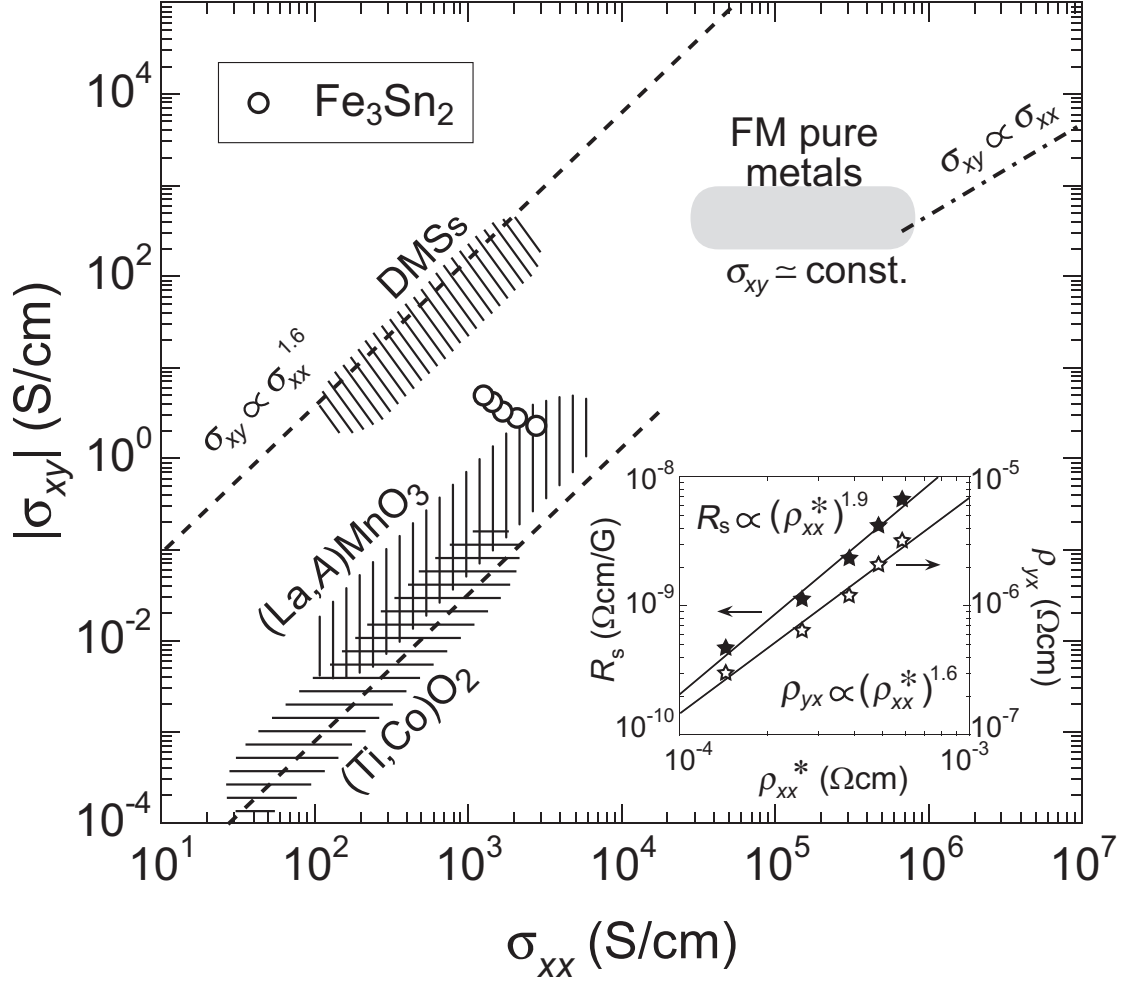


FIG. 5: Absolute value of the anomalous Hall conductivity $|\sigma_{xy}|$ as a function of longitudinal conductivity σ_{xx} in Fe₃Sn₂ (open circle), ferromagnetic (FM) pure metals, diluted magnetic semiconductors (DMSs), perovskite manganites ((La, A)MnO₃), and Co-doped rutile TiO₂. The inset shows the R_s and ρ_{yx} ($= \rho_H$) as a function of ρ_{xx}^* ($= \rho_{xx} - \rho_0$) for Fe₃Sn₂.